

Shifted laser surface texturing for bearings applications

This content has been downloaded from IOPscience. Please scroll down to see the full text.

2017 J. Phys.: Conf. Ser. 843 012076

(<http://iopscience.iop.org/1742-6596/843/1/012076>)

View [the table of contents for this issue](#), or go to the [journal homepage](#) for more

Download details:

IP Address: 147.228.174.200

This content was downloaded on 02/06/2017 at 13:28

Please note that [terms and conditions apply](#).

You may also be interested in:

[Optimum dimple diameter for friction reduction with laser surface texturing: the effect of velocity gradient](#)

Christian Greiner, Tobias Merz, Daniel Braun et al.

[Acoustic Emission in Laser Surface Cleaning for Real-Time Monitoring](#)

Yong-Feng Lu and Yoshinobu Aoyagi

[Laser induced twin-groove surface texturing based on optical fiber modulation](#)

Dameng Liu, Hui Wang, Kang Su et al.

[Bio-inspired scale-like surface textures and their tribological properties](#)

Christian Greiner and Michael Schäfer

[Laser Surface Cleaning in Air: Mechanisms and Applications](#)

Yong-Feng Lu, Yoshinobu Aoyagi, Mikio Takai et al.

[Estimation of Surface Absorptivity and Surface Temperature in Laser Surface Hardening Process](#)

Yann-Shouh Sun, Cheng-I Weng, Tei-Chen Chen et al.

[Holographic interference for microfabrication](#)

Jintang Huang, Stefan Beckemper, Arnold Gillner et al.

[Determination of the Insoluble Aluminum Content in Steel Samples by Using Laser-Induced Breakdown Spectroscopy](#)

Liu Jia, Jia Yunhai, Zhang Yong et al.

[Use of structured surfaces for friction and wear control on bearing surfaces](#)

Ling Wang

Shifted laser surface texturing for bearings applications

Š Houdková¹, P Šperka², M Repka², J Martan¹ and D Moskal¹

¹University of West Bohemia, new Technology Research Centre, Univerzitní 8, Plzeň, 30614

²Brno University of Technology, faculty of Mechanical Engineering, Technická 2, Brno, 61669

houdkov@ntc.zcu.cz Type the corresponding author's e-mail address here

Abstract. The laser surface texturing (LST) technologies, based on creation of micro-pattern with pre-defined geometry can positively influence both the friction and wear of tribo-elements. In practice, the integration of LST technology is often limited due to its slowness. The new method, so called shifted laser surface texturing (sLST) with increased process speed was developed to make the technology more attractive for the industrial application. In the paper, the texture created by sLST technology was applied onto the steel samples and Al-Sn-Si surface of sliding bearings. Both block-on-ring (ASTM G-77) laboratory tests of steel samples and high-loaded working application tests on Al-Sn-Si bearings surface were carried out to evaluate the influence of texture on tribological behaviour. The ASTM G-77 laboratory tests showed a positive effect of the texture on friction behaviour. Under the high-loaded testing conditions, the positive effect was observed in initial stages of the tests, decreasing the torque of textured bearings compared to the untreated one. Lately, the texture was worn out and have no influence on the overall wear of the bearings. Based on the above mentioned observations, the use of alternative bearing material with higher hardness or application of protective layer over the created texture was suggested to exploit the texture benefits.

1. Introduction

In recent years, the utilization of lasers as a tools for surface modification became popular. Apart from the most widespread technologies, such as laser hardening or cladding for wear-resistant applications, a more sophisticated surface treatment can be applied to modify the surface properties.

The laser surface texturing (LST) is a technology of creation of pattern with defined geometry on the surface of treated parts. Depending on the shape of the texture, the surface can receive a new functional properties, such as hydrophobicity [1, 2], adhesion of subsequent layers [3,4], light absorption [5,6], self-cleaning [5] or tribological performance [7].

The principle of LST can be described as a removing of material by ablation process. Using the scanning optical systems for movement of the laser beam on the workpiece on predefined trajectories, the desired texture geometry can be created [8]. Although, the LST is a promising technology increasingly used in industrial applications, there are some limitations of current LST methods, such as heat accumulation and oxidation [9-11], plasma shielding effect [12] or precision at high speed [13]. To overcome the limitations the new method, called shifted laser surface texturing (sLST) was developed,



enables effective use of existing state-of-the-art high power ultrashort pulse lasers. This surface texturing process, which utilises the average power and repetition rate of the ultrashort pulsed laser source more effectively than current methods via spreading the pulses temporally across the component to be textured, enables precise laser surface texturing to be performed, at industrially relevant speeds, whilst ensuring minimal thermal degradation of the component's surface. In detail, the sLST is described in [14,15].

The tribological performance is the matter of interest of many industrial applications such as bearings [16], shafts, piston rings [17] etc. Many studies exist concerning the influence of surface texturing on the sliding performance. They are addressing the influence of texture geometry on the shape of the sliding behavior experimentally [18] [19] [20], or using numerical models [21].

From the published work, the factors playing significant role can be identified, such as the density of textured area or the diameter to depth ratio of created dimples [22] [23]. Besides them, the quality of the texture, namely the amount of re-deposited material inside [24] or around [25] the created objects, is crucial for success in effort to decrease the friction and wear.

Based on the above mentioned studies, the texture design with potential to decrease the friction in the boundary/mixed lubrication mode was chosen and applied on the surface of bearings steel samples and Al-Sn-Si bearings. The laboratory ASTM G-77 test as well as the high loaded test simulating the bearings working conditions were performed to verify the positive effect of the created texture on the sliding behavior.

2. Experimental

The texture design (Fig. 1) was chosen based on the literature review and the results of preliminary study of sliding properties [26]. The diameter of the dimples was set $78\ \mu\text{m}$, the depth varied between $6.5\text{-}7\ \mu\text{m}$. The distance between the dimples centers was $200\ \mu\text{m}$, leading to the texture area density of 12%.

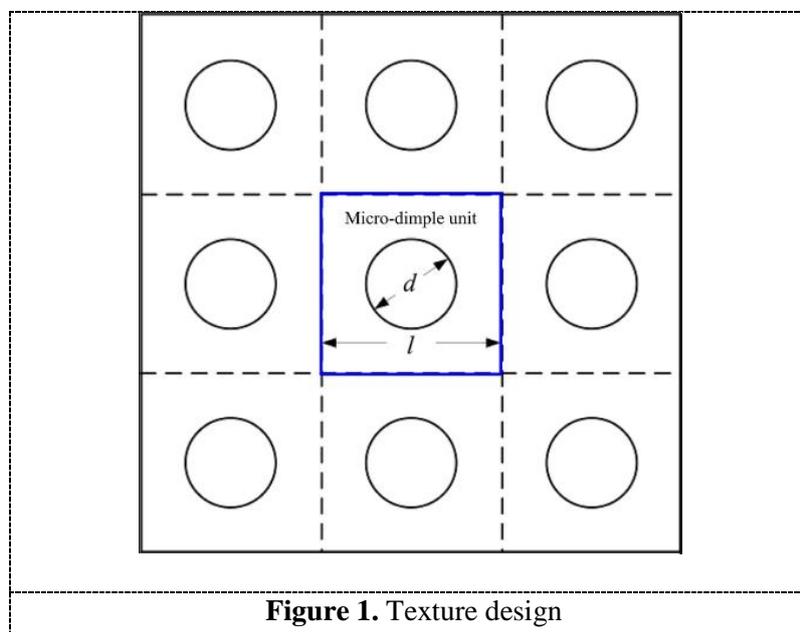


Figure 1. Texture design

The texture was applied on the outer surface of Timken A4138 rings, 35 mm outer diameter, made from the bearing steel (Fig. 2), and on the inner surface of Al-Sn-Si half bearings with inner diameter of 56 mm (Fig. 3).

The geometrical preciseness of the textured surface was evaluated by optical profilometer Bruker Contour GT X8.



Figure 2. Textured Timken A4138 ring

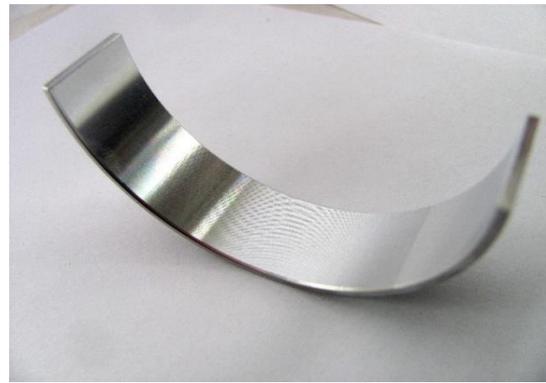


Figure 3. Textured half bearing

2.1. Texturing procedure

The Picosecond slab laser EdgeWave PX25-2-G with wavelength 532 nm, average power 14 W, pulse duration 10 ps and maximum pulse energy 100 μ J was used for texturing. The laser was equipped with scanning head with f-theta objective. The objective focal length was 255 mm, the laser spot diameter was 28 μ m. Laser beam movement is produced by Scanlab software in connection with scanhead intelliSCAN® III 14. Maximal speed of laser moving is 8 m/s.

The sLST process of rings and bearings texturing was divided into several rectangular areas composed of array of dimples. Every textured rectangle was formed by sequential repetition of laser scanning processing of linear raster of individual spots – one spot per dimple in one repetition (Fig. 4). Between each repetition, the raster is slightly shifted to place next laser pulse with certain overlap. Individual spots are collected in four rings for every dimple. Whole quantity of the spots in one dimple is 127 laser pulses. Frequency of the laser pulses generation was 10 kHz, pulse energy 30 μ J and laser beam movement 2 m/s. Full process of forming of one textured rectangle contains 127 rasters (equal to the laser spots for one dimple) multiplied by 6 repetitions. After full finishing one of the textured rectangle the bearing was rotated to the next non-textured surface area for providing the next sLST processing. Rotations of the bearings were provided with step equal to the textured rectangular width 2 – 4 mm, depending on the bearing geometry. Speed of one movement between neighbor rectangles was set 50 degree per second.

Correct connection of the first and last textured rectangles was controlled by optical microscopy on Hirox 3D microscope. Total quantity of rectangles for full textured surface on ring with diameter 3.5 cm was 77 movements.

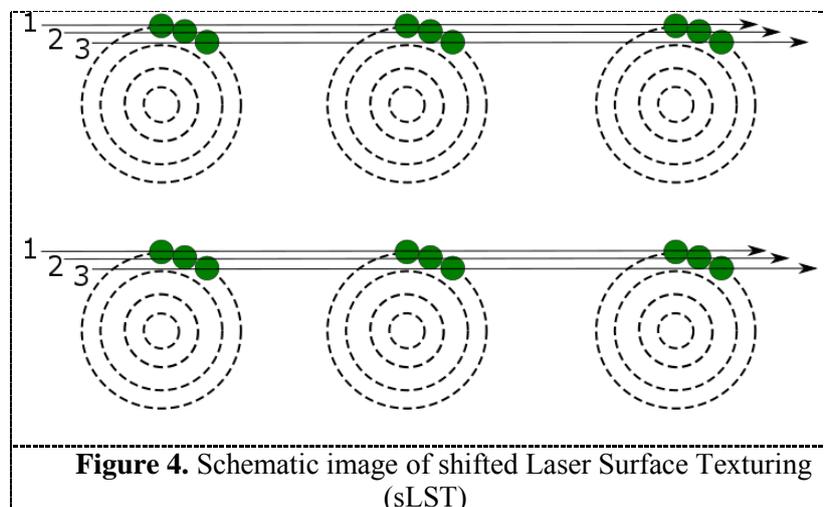


Figure 4. Schematic image of shifted Laser Surface Texturing (sLST)

2.2. Laboratory Block-on-Ring testing

The RTEC (RTEC Instruments, USA) universal tribometer was used to compare the sliding behavior of textured and non-textured Timken A4138 rings samples. The Block-on-Ring test, according to ASTM G-77 was carried out on non-textured sample (twice) and 3 samples with texture. The testing parameters are summarized in the Table 1. Dip lubrication of the rings in mineral base oil was used and temperature of oil in the bath was recorded. All tests were started at similar temperature of the oil in the bath. During testing, the coefficient of friction (COF) was recorded. The surface topography was evaluated before and after the test.

Table 1. Testing parameters of “block-on-ring” testing

Item	Dimensions	Unit
Samples	Timken A4183, ϕ 35	mm
Counterparts	Block, 100Cr6, Ra 0.4	μm
Load	40	N
Speed (RPM)	10,20,50,100,200,400,700,1000,1500	min^{-1}
Intervals for each speed	10 (6 for 1000 and 1500 min^{-1})	s
Temperature	25 ± 2	$^{\circ}\text{C}$
Lubricant	Mineral oil R834/90 (dyn. viscosity 0.115 Pas)	
Repetition	3 times from low speed to highest and vice versa	

2.3. Harsh condition testing

The testing system, developed in Daido Metal CO., Ltd. –The European Technical Center, was used to evaluate the behavior of Al-Sn-Si textured half bearings. The system is composed of a driving part where the shaft rotation can achieve up to 10 000 rpm, with loading and lubrication systems. For overloading conditions, the clutch is integrated. The loading system is applied by a hydraulic system able to simulate static and dynamic testing with force amplitude 100 kN and frequency 60 Hz. Bearings were tested for their wear resistance and anti-seizure properties.


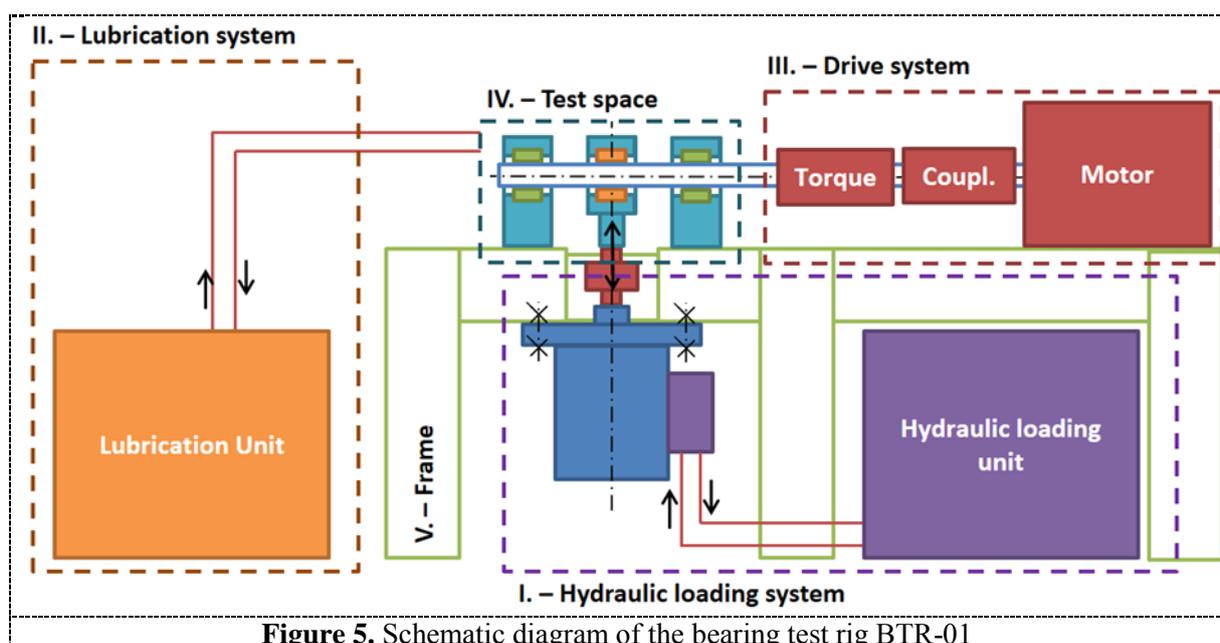


Figure 5. Schematic diagram of the bearing test rig BTR-01

2.3.1. Wear Test. Wear test conditions are described below in Table 2. The test machine was set for repeated start/stop cycling conditions for rotation of shaft to 1 m/s similar to hybrid vehicle or start-stop engines to be reproduced, i.g. with frequent start-ups when the oil film is sparse to promote bearing wear. The test mode is shown in Figure 6. Constant static load was set to the specific load (or nominal pressure) 5 MPa with limited oil flow supply of lubricant at room temperature. The wear volume was calculated from the measuring of the weight and the dimensional checks.

Table 2. Testing parameters of wear test

Item	Dimensions	Unit
Samples	Al-Sn-Si, ϕ 35W15xT1.5	mm
Counterparts	Shaft, Carbon steel, $Rz \leq 0.1$	μm
Test specific load	5	MPa
Sliding speed	1	m/s
Test duration	20	hour
Lubricant	VG05	
Oil inlet temperature	Room temperature	
Oil flow	2.0	ml/min
Test mode	Start-stop	

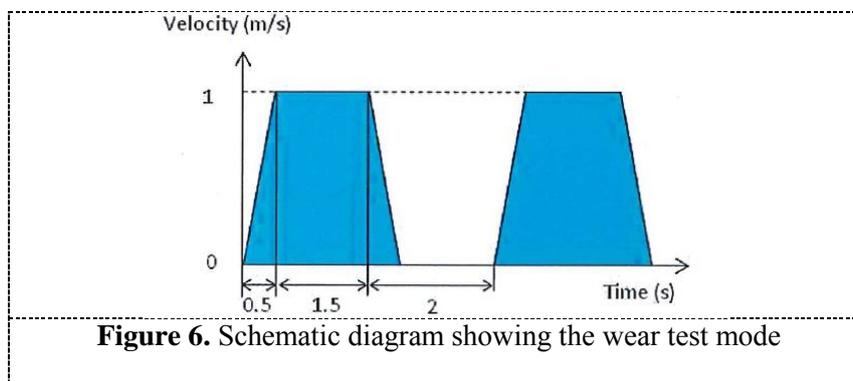

3. Results and discussion

3.1. Laboratory Block-on-Ring testing

The results of the Block-on-Ring testing summarized in the Figure 7. The average value of coefficient of friction and standard deviation is calculated from 6 measured values (each test was performed 3 times, the rotational speed was changed up and down).

From the measured results it can be seen, that the two rings (Textured 1 and Textured 2) showed lower friction in the area of lower speeds (up to 1000 min^{-1}). For higher speeds, the textured surfaces has the tendency to increase the friction compare to non-textured surface. According to the shape of the Stribeck curve and measured values, it can be said that the textured surface improves the friction in the mixed lubrication mode.

The results of Textured 2 sample showed opposite manner, but it has to be mentioned, that the behavior of the Textured 2 samples was not standard at all. According to optical profilometers

measurements it can be estimated, that the sample differ from the others namely in the cylindricity of the basic geometry.

The same data are replotted against lubrication parameter in Fig. 8. Lubrication parameter is a ratio of lubrication layer thickness and the composite surface roughness. For the given testing configuration and materials, using the Hertz contact theory, film thickness prediction formula [27] and composite roughness (R_q 0.45 μm for the block; R_q 0.3 μm for the ring), the lowest measured COF was reached at the lubrication parameter in the range 3.5-4. It is known, that to full separation of the surfaces the value of lubrication parameter higher than 3 is needed [28].

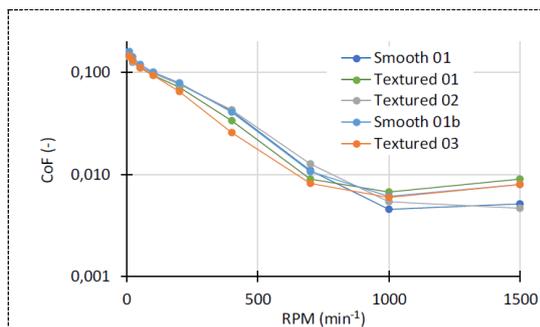


Figure 7. Comparison of COF for all measured Timken A4183 samples in dependence on the rotation speed

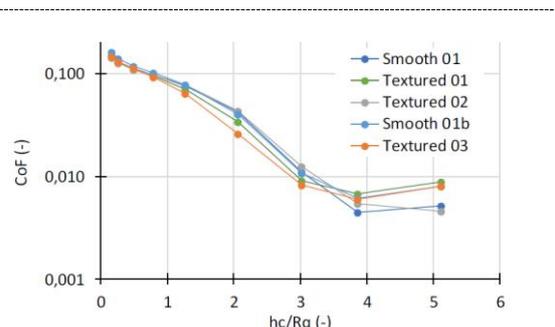


Figure 8. Comparison of COF for all measured Timken A4183 samples in dependence on the lubrication parameter

Discussing the choice of testing approach, it has to be mentioned, that the block-on-ring configuration, with line contact, is not the same as it is in the case of hydro-dynamically lubricated plain bearings. According to the Hertz theory, for the given testing configuration, the contact area is 72 μm wide. The value is smaller than the diameter of dimples in the texture (75-85 μm). Therefore, to improve performance of textures, a modification lead to wider contact area would be appreciated– e.g. use of a part of inner cylinder diameter as a counterpart geometry.


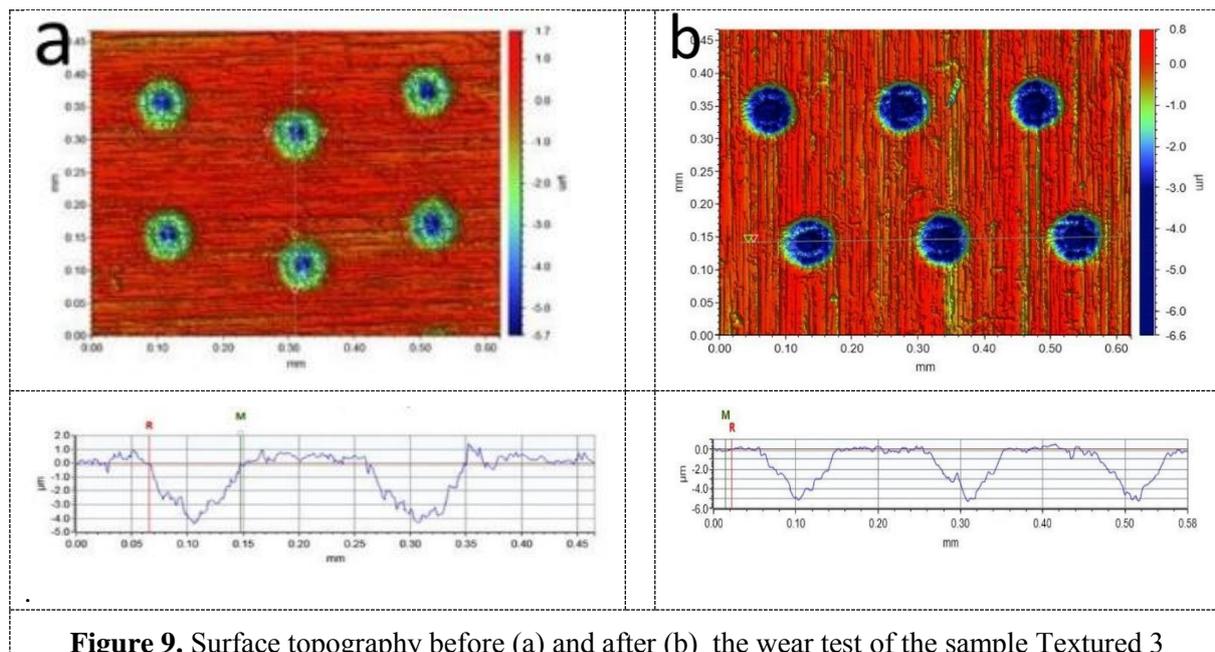


Figure 9. Surface topography before (a) and after (b) the wear test of the sample Textured 3

No wear of textured surfaces was recording during the block-on-ring tests. In the Figure 9, the comparison of the Textured 3 surface profile before (Fig. 9a) and after (Fig. 9b) test can be seen. Similar results were obtained also for the others samples.

3.2. Harsh condition testing

3.2.1. *Wear test results.* From the wear tests results (Fig. 10) it is obvious, that the texture was worn-out from the surface quite soon after the running of the tests, since the depth of textures varied between 6.5-7 μm . There is no significant difference in wear amount between the textured bearings and the untreated bearings.

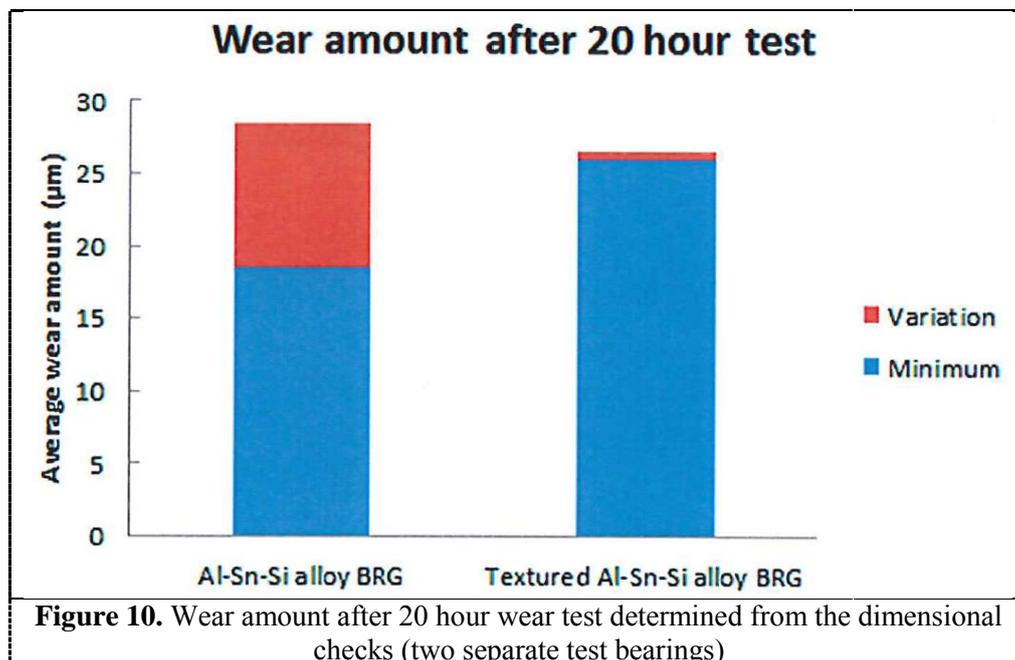

The wear occurs mostly around the main loaded area. The dimples in this area were completely removed after the wear test. The remaining textured surfaces were measured for surface topography to observe the evolution of the wear (Figure 11). The scans were carried out near the radial edge of the bearing, as there is less wear around that and the interface can be observed. Closer to the main area, no remaining texture was observed.

During the test, the torque on shaft was recorded. In the Figure 12, the comparison between the untreated and textured bearings is shown in initial stage of stages of the test (Fig 12a) and after one hour of testing (Fig. 12b). While at the initial stages of the test the positive effect of the texture is obvious, just a little difference in torque between non-textured and textured bearings was found after one hour of testing due to worn out of the texture.

4. Conclusions

The efficient sLST method proves its suitability to produce the texture on the parts surface, which can positively influence the sliding behavior. The potential of the texture to decrease the friction in boundary lubrication mode was proved by both laboratory testing as well as by the testing under harsh conditions, where the torque of the shaft was decreased without the negative influence on the bearing wear. The lower measured torque in initial stages of star-stop test could be explained by faster oil formation during running. Although the positive effect of the texture was recorded namely in the initial stages of the test due to the fast worn-out, the very harsh condition of the test has to be taken into account.

Under real working conditions, the time to worn out of the texture is expected to be much longer. If the sLST method will be applied on more wear resistant bearing material than the Al-Sn-Si alloy, the lifetime of the textured surface can be also increased.

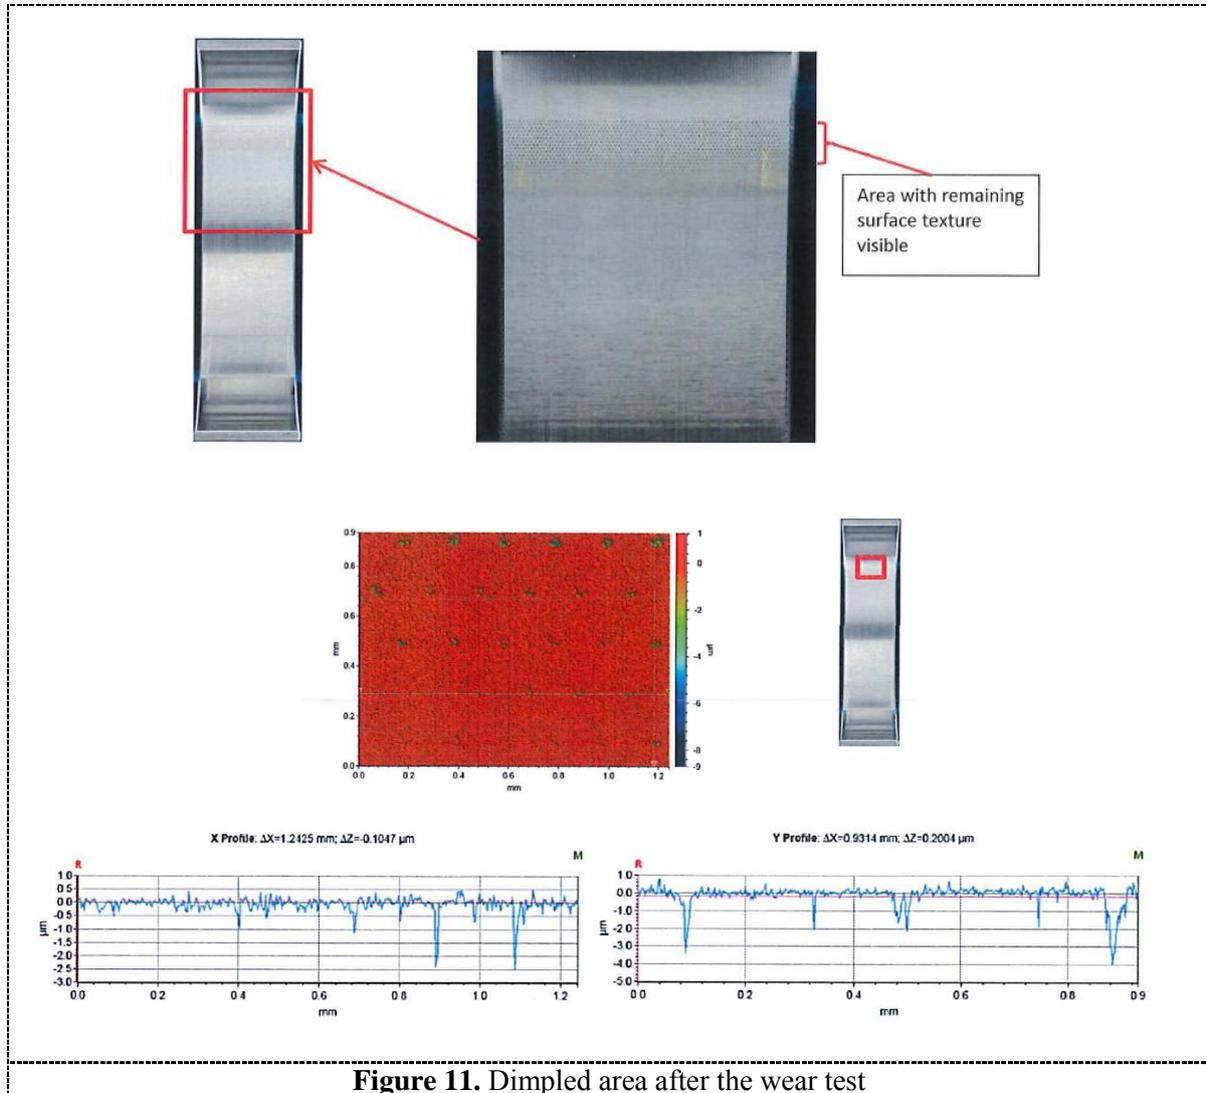


Figure 11. Dimpled area after the wear test

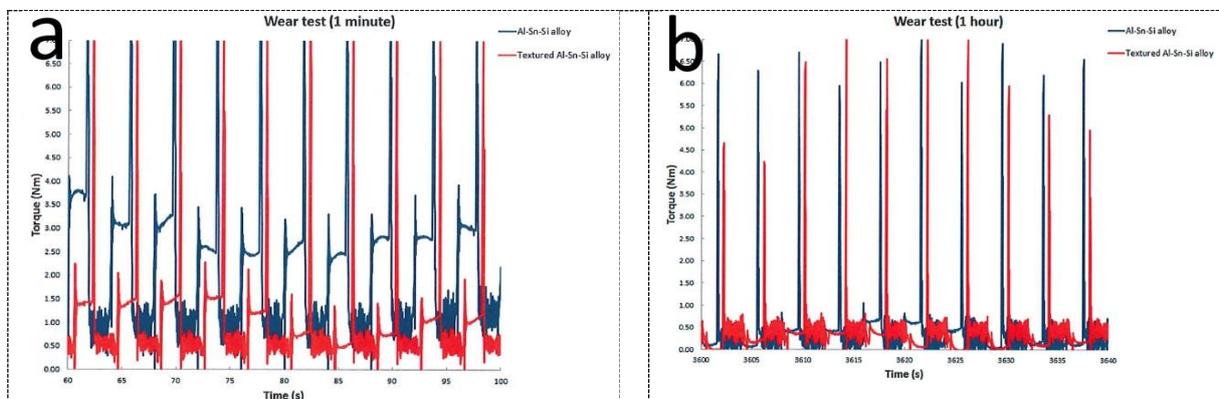


Figure 12. Torque measured during initial stage (a) and after 1 hour of testing (b)

Acknowledgement

The result was developed within the CENTEM project, reg. no. CZ.1.05/2.1.00/03.0088, co-funded by the ERDF as part of the Ministry of Education, Youth and Sports of the Czech Republic OP RDI program and, in the follow-up sustainability stage, supported through CENTEM PLUS (LO1402) by financial means from the Ministry of Education, Youth and Sports under the "National Sustainability Program I" and project SGS-2016-005.

The authors thank to Daido Metal Co-Ltd.-The European Technical Center for use of their testing rig BTR-01.

References

- [1] Yilbas B S, Khaled M, Abu-Dheir N, Aqeeli N and Furquan S Z 2013 Laser texturing of alumina surface for improved hydrophobicity *Appl. Surf. Sci.* **286** 161–70
- [2] Shum P W, Zhou Z F and Li K Y 2014 To increase the hydrophobicity, non-stickiness and wear resistance of DLC surface by surface texturing using a laser ablation process *Tribol. Int.* **78** 1–6
- [3] Kromer R, Costil S, Cormier J, Berthe L, Peyre P and Courapied D 2016 Laser Patterning Pretreatment before Thermal Spraying: A Technique to Adapt and Control the Surface Topography to Thermomechanical Loading and Materials *J. Therm. Spray Technol* **25** 401–10
- [4] Kromer R. et al. 2015 Laser surface patterning to enhance adhesion of plasma sprayed coatings *Surf. Coatings Technol* **278** 171–82
- [5] Vorobyev A Y and Guo C 2015 Multifunctional surfaces produced by femtosecond laser pulses *J. Appl. Phys.* **33103** 6–11
- [6] Zheng B, Wang W, Jiang G and Mei X 2016 Fabrication of broadband antireflective black metal surfaces with ultra-light-trapping structures by picosecond laser texturing and chemical fluorination *Appl. Phys. B* **122** 180
- [7] Etsion I 2005 State of the Art in Laser Surface Texturing *J. Tribol. Trans. ASME* **127** 248
- [8] Jaeggi B, Neuenschwander B, Zimmermann M, Loor R D and Penning L 2014 High throughput ps-laser micro machining with a synchronized polygon line scanner *8th International Conference on Photonic Technologies LANE 2014 Bayerisches Laserzentrum GmbH Germany* 1–8
- [9] Weber R et al 2014 Heat accumulation during pulsed laser materials processing *Opt. Express* **22** 11312–24
- [10] Bauer F, Michalowski A, Kiedrowski T. and Nolte S 2015 Heat accumulation in ultra-short pulsed scanning laser ablation of metals *Opt. Express* **23** 1035–43
- [11] Schonlau T, Hebel R, Pause S and Mayer G 2014 Machining strategies for versatile ultra-short pulse laser applications. *8th International Conference on Photonic Technologies LANE 2014 Bayerisches Laserzentrum GmbH Germany* 1–4
- [12] Bulgakova N M et al 2014 Impacts of ambient and ablation plasmas on short- and ultrashort-pulse laser processing of surfaces *Micromachines* **5** 1344–72
- [13] Moskal D, Kučera M, Smazalová E, Houdková Š and Kromer R 2015 Application of Shifted Laser Surface Texturing *METAL 2015 - 24th International Conference on Metallurgy and Materials* Tanger Ltd. Czech Republic 1016–21
- [14] Moskal D, Martan J, Kučera M, Houdková Š, Kromer R, 2016 Picosecond Laser Surface Cleaning of AM1 Superalloy *Physics Procedia* **83** 249-57
- [15] Martan J, Moskal D, Kučera M 2017 Laser surface texturing for large area functional surfaces, *Nature Communications*, Preprint
- [16] Brizmer V, Kligerman Y and Etsion I 2003 A Laser Surface Textured Parallel Thrust Bearing *Tribol. Trans* **46** 397–403
- [17] Kligerman Y, Etsion I and Shinkarenko A 2005 Improving Tribological Performance of Piston

- Rings by Partial Surface Texturing *J. Tribol.* **127** 632
- [18] Galda L, Pawlus P, and Sep J 2009 Dimples shape and distribution effect on characteristics of Stribeck curve *Tribol. Int.* **42** 1505–12
- [19] Wan Y and Xiong D S 2008 The effect of laser surface texturing on frictional performance of face seal *J. Mater. Process. Technol.* **197** 96–100
- [20] Li K, Yao Z, Hu Y and Gu W 2014 Friction and wear performance of laser peen textured surface under starved lubrication *Tribol. Int.* **77** 97–105
- [21] Gropper D, Wang L and Harvey T J 2016 Hydrodynamic lubrication of textured surfaces: A review of modeling techniques and key findings *Tribol. Int.* **94** 509–29
- [22] Mishra S P and Polycarpou A A 2011 Tribological studies of unpolished laser surface textures under starved lubrication conditions for use in air-conditioning and refrigeration compressors *Tribol. Int.* **44** 1890–1901
- [23] Braun D, Greiner C, Schneider J and Gumbsch P 2014 Efficiency of laser surface texturing in the reduction of friction under mixed lubrication *Tribol. Int.* **77** 142–47
- [24] Zuhlke C A, Anderson T P and Alexander D R 2013 Formation of multiscale surface structures on nickel via above surface growth and below surface growth mechanisms using femtosecond laser pulses *Opt. Express.* **21** 8460–73
- [25] Dumitru G, Romano V, Weber H P, Haefke H, Gerbig Y and Pflüger E 2000 Laser microstructuring of steel surfaces for tribological applications *Appl. Phys. A Mater. Sci. Process.* **70** 485–87
- [26] Houdková Š, Martan M, Moskal D and Muzika L 2017 Laser technologies for modification of functional surface properties *Manufacturing technology* Preprint
- [27] Pan P, Hamrock B J 1989 Simple Formulas for Performance Parameters Used in Elastohydrodynamically Lubricated Line Contacts *J. Tribol.* **111** 246-51.
- [28] Tallian T E 1967 On Competing Failure Modes in Rolling Contact *ASLE Transactions* **10** 418-39.